

A Universal Phase Diagram for PMN- x PT and PZN- x PT

P. M. Gehring

NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, Maryland 20899

W. Chen and Z.-G. Ye

Department of Chemistry, Simon Fraser University, Burnaby, British Columbia, Canada V5A 1S6

G. Shirane

Physics Department, Brookhaven National Laboratory, Upton, New York 11973

(Dated: February 2, 2008)

The phase diagram of the $\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ and PbTiO_3 solid solution (PMN- x PT) indicates a rhombohedral ground state for $x \leq 0.32$. X-ray powder measurements by Dkhil *et al.* show a rhombohedrally split (222) Bragg peak for PMN-10%PT at 80 K. Remarkably, neutron data taken on a single crystal of ‘the same compound with comparable q -resolution reveal a single resolution-limited (111) peak down to 50 K, and thus no rhombohedral distortion. Our results suggest that the structure of the outer layer of these relaxors differs from that of the bulk, which is nearly cubic, as observed in PZN by Xu *et al.*

PACS numbers: 77.84.Dy, 77.80.Bh, 64.70.Kb, 61.12.-q

The well-known relaxor $\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ (PMN) retains an average cubic structure down to 5 K when cooled in zero field (ZFC). [1, 2, 3] In this respect PMN represents a puzzling anomaly among the related complex-perovskite relaxors PMN- x PT and PZN- x PT ($\text{M}=\text{Mg}$, $\text{Z}=\text{Zn}$, $\text{PT}=\text{PbTiO}_3$), all of which are believed to exhibit a rhombohedral phase at low temperatures and low PT concentrations. [4, 5, 6, 7] X-ray scattering measurements performed on a series of PMN- x PT compounds by Ye *et al.*, for example, demonstrate the presence of a clear rhombohedral distortion for PT concentrations as low as $x = 0.05$, [8] while Lebon *et al.* have reported a detailed x-ray study of the cubic-to-rhombohedral phase transition in single crystal PZN with high q -resolution. [9] An interesting comparison between PMN and PMN-10%PT was performed by Dkhil *et al.* using both x-ray and neutron scattering methods on powder and single crystal samples which indicate the presence of competing tetragonal and rhombohedral order. [10] In PMN these never result in a ferroelectric distortion, but in PMN-10%PT a rhombohedral distortion is observed below a critical temperature $T_c = 285$ K. From these studies, PMN appears to be the exception in which a ferroelectric phase is never established.

Recent results, however, are now beginning to point towards a radically different physical picture. Neutron scattering data obtained by Ohwada *et al.* on a single crystal of PZN-8%PT suggest the presence of a low-temperature phase in the PZN- x PT family that is not rhombohedral, but that has an average cubic structure. [11] This new phase was termed ‘‘Phase X.’’ Striking evidence of this new phase was subsequently discovered by Xu *et al.* in single crystal PZN where both the rhombohedral phase and Phase X were observed. [12] More intriguing is the fact that the visibility of a given phase

depends on the x-ray energy, and thus the penetration depth.

In this Letter we report the results of a high q -resolution neutron scattering study of single crystal PMN-10%PT that traces the evolution of the (111) Bragg peak from the cubic phase above $T_c = 285$ K down to 50 K. In stark contrast to the findings of Dkhil *et al.* we observe no splitting of the (111) peak at any temperature in PMN-10%PT, as *must* occur under a rhombohedral transformation. Further, the (111) peak is nearly resolution-limited at low temperature, and comparable in width to that observed by Dkhil *et al.* at (222) in the cubic phase. The implications of these results are significant. Combined with the results on PZN-8%PT and PZN obtained by Ohwada *et al.* and Xu *et al.* our findings support the diametrically opposite point of view in which PMN is the rule, not the exception. In other words, none of the relaxors in either the PMN- x PT or PZN- x PT family transforms to a rhombohedral phase at low temperatures. Instead they transform into Phase X.

The neutron scattering data presented here were obtained on the BT9 triple-axis spectrometer located at the NIST Center for Neutron Research. The diffuse scattering near the (300) Bragg peak was measured at a fixed neutron energy $E_i = E_f = 14.7$ meV ($\lambda = 2.36$ Å) using the (002) reflection of highly-oriented crystals of pyrolytic graphite (HOPG) as monochromator and analyzer. Horizontal beam collimations were 40'-46'-S-40'-80' (S = sample). Measurements of the (111) Bragg peak were performed in a non-standard spectrometer configuration using the (220) reflection of a perfect Ge crystal as analyzer, tighter beam collimations of 10'-46'-S-20'-40', [13] and a lower neutron energy of 8.5 meV to achieve an extremely sharp q -resolution of 0.0018 rlu (1 rlu = $2\pi/a = 1.5576$ Å⁻¹) FWHM. The (220) reflection of Ge was cho-

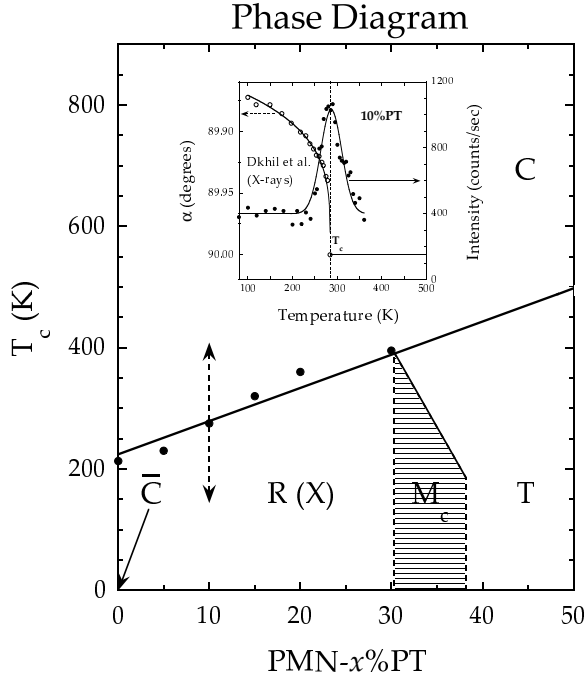


FIG. 1: Currently accepted zero-field phase diagram of PMN- x PT. [4, 5] Inset shows the temperature dependence of the rhombohedral angle α and diffuse scattering measured with x-rays by Dkhil *et al.* on PMN-10%PT (Ref. [10]). Lines are guides to the eye.

sen because its d -spacing most closely matches that of the PMN-10%PT (111) Bragg reflection. [14]

A high quality single crystal of PMN-10%PT was by a top-seeded solution growth technique. [15] The growth conditions were determined from the pseudobinary phase diagram established for PMN and PbO. The crystal, which weighs 2.65 gm (0.33 cm^3), is an irregular parallelepiped with dimensions $11.3 \times 9.2 \times 4.1\text{ mm}^3$, the largest facets of which are oriented approximately normal to the cubic [100] direction. At 500 K the crystal mosaic measured at (200) is less than 0.06° full-width at half-maximum (FWHM). The crystal was mounted on a boron nitride post with the $[01\bar{1}]$ axis oriented vertically, giving access to reflections of the form (hll) . The sample holder assembly was mounted inside the vacuum space of a high-temperature closed-cycle ^3He refrigerator that was then positioned and fixed onto the goniometer of the BT9 spectrometer.

In Fig. 1 we present the currently accepted phase diagram for PMN- x PT, which shows a cubic (C) to rhombohedral (R) phase transition for PbTiO_3 concentrations x less than $\approx 32\%$. [4, 5] The solid circles represent measured values of T_c reported by various authors (see Fig. 4 of Ref. [8]), while the solid line is merely a guide to the eye. The lone data point for PMN ($x = 0$) corresponds to the first-order R-to-C phase transition that occurs at 213 K after first cooling in a field $E \geq 1.7\text{ kV/cm}$. [3] As

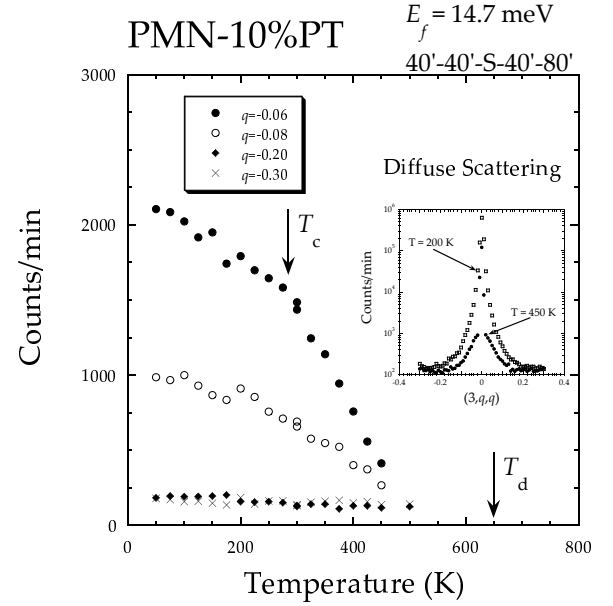


FIG. 2: Neutron diffuse scattering intensity measured as a function of temperature at $\vec{Q} = (3, q, q)$ on a PMN-10%PT single crystal. The inset shows the full diffuse scattering profile measured along the $[011]$ direction (transverse to $\vec{Q}$) at 200 K and 450 K.

PMN retains an average cubic structure below this temperature when zero-field cooled (ZFC), we use the notation $\bar{C}$ shown by the arrow. At higher concentrations, PMN- x PT exhibits a narrow region of monoclinic (M_c) phase discovered by Noheda *et al.* [5] that lies next to the well-known morphotropic phase boundary (MPB) separating the M_c phase from the tetragonal (T) phase. The 10%PT concentration is indicated by the vertical dashed line in the phase diagram.

The inset to Fig. 1 shows the temperature dependence of the rhombohedral angle α (left-hand scale), as well as that of the diffuse scattering (right-hand scale) near the (300) Bragg peak (q not specified), for PMN-10%PT measured by Dkhil *et al.* using x-ray diffraction. [10] The data for α are consistent with the occurrence of a first-order phase transition at 285 K, while the diffuse scattering, which is characterized by the authors as critical behavior, displays a very broad peak centered at this same temperature.

Neutron diffuse scattering results obtained on the single crystal of PMN-10%PT were obtained at the NCNR using relatively coarse horizontal beam collimations. These data, shown in Fig. 2 as a function of temperature, were measured along the $[011]$ direction near (300) at different values of the reduced wavevector q spanning the range $-0.30\text{ rlu} \leq q \leq 0.30\text{ rlu}$. A break in the slope of the diffuse scattering is evident for $q = -0.06\text{ rlu}$ at a temperature near T_c (shown by the arrow). However there is no evidence of the peak in intensity at T_c found by x-rays. Instead, the diffuse scattering intensity in-

creases monotonically with decreasing temperature down to 50 K at all values of q studied. These data refute the idea that the diffuse scattering in PMN-10%PT is critical in nature. In fact, as shown in the inset to Fig. 2, the diffuse scattering is quite strong at 450 K, far above $T_c = 285$ K. The diffuse scattering at this temperature appears as a very broad peak, with a maximum count rate of just under 10^3 counts/min, superimposed on top of the much narrower (300) Bragg peak which is roughly two orders of magnitude larger. In pure PMN the diffuse scattering is known to disappear at the Burns temperature $T_d = 600 - 650$ K [16] above which polar nanoregions (PNR) no longer exist. [17] The approximate corresponding value of T_d for PMN-10%PT is shown by the arrow at 650 K.

Using the high q -resolution configuration described earlier, radial and transverse q -profiles of the (111) Bragg peak of the PMN-10%PT crystal were measured down to 50 K. Two radial scans, one in the cubic phase at 325 K, and one in the rhombohedral phase at 100 K, are shown side-by-side in Fig. 3. Above these two scans are shown the corresponding x-ray scans from Dkhil *et al.* The horizontal scales for the x-ray data, which were measured at (222), have been reduced by a factor of two to allow for direct comparison to the neutron data, which were measured at (111). At high temperatures both x-ray and neutron data show the presence of a single resolution-limited peak, consistent with a cubic lattice. The horizontal bars represent the calculated BT9 instrumental q -resolution FWHM, and show that x-ray and neutron resolutions are comparable. At 80 K, the x-ray data show a clear splitting of the (222) peak. At roughly the same temperature, however, the neutron data show a single peak that is only slightly broader than resolution. Remarkably, these data contradict the finding that PMN-10%PT is rhombohedral below T_c .

Our findings strongly support the opposite point of view in which *none* of the relaxors in the PMN- x PT family exhibit a rhombohedral phase in zero-field below T_c . The high-energy x-ray study of Xu *et al.* demonstrates the presence of a $\approx 50 \mu\text{m}$ thick ($1 \mu\text{m} = 10^{-6}\text{m}$) outer layer in the closely related relaxor PZN that undergoes a rhombohedral distortion at low temperatures, while the interior volume of the crystal does not. [12] We believe this to be the case for PMN-10%PT as well. The presence of such an outer layer would reconcile the x-ray and neutron data shown in Fig. 3 since the 8.9 keV x-rays penetrate $\approx 10 \mu\text{m}$ into the sample whereas neutrons probe the entire crystal volume. It would also explain why the diffuse scattering peak observed with x-rays at T_c shown in Fig. 1 is absent when measured with neutrons (Fig. 2). Evidence for this outer layer is visible at the base of the 100 K neutron data shown in Fig. 3 where an asymmetric broadening is observed. While these data are insufficient to extract quantitative information about the thickness of the outer layer, they can be fitted to two Lorentzian

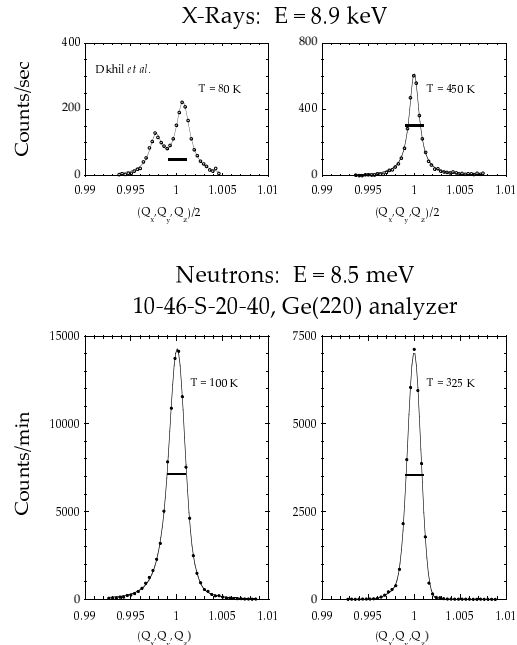


FIG. 3: Comparison of x-ray measurements by Dkhil *et al.* at (222) (top) [10] and our neutron measurements at (111) (bottom) on PMN-10%PT. The horizontal scale of the x-ray data have been reduced by a factor of two to allow direct comparison with the neutron (111) data. Solid bars indicate the BT9 instrumental q -resolution FWHM.

peaks (representing the rhombohedral phase), and one Gaussian peak (for Phase X). The solid line shows a high quality of fit.

In light of the neutron results of Ohwada *et al.* obtained on PZN-8%PT [11] and Xu *et al.* on PZN, [12], we speculate that there is no bulk zero-field rhombohedral phase in PZN- x PT either. We propose instead a new and universal phase diagram for both the PMN- x PT and PZN- x PT systems, as shown in Fig. 1, in which the rhombohedral phase is replaced by Phase X. This scenario is attractive not just because it reconciles the PMN anomaly, but also because it explains the neutron scattering results of Wakimoto *et al.* which demonstrate the presence of a soft mode, and thus a ferroelectric polarization, below T_c in PMN, [18] and also of Stock *et al.* who showed that PMN and PZN exhibit soft modes with identical temperature dependences below T_c . [19]

While the origin of an outer layer presents an interesting question, we do not believe it is of fundamental importance to the underlying properties of the relaxor compounds. Rather, we feel that the seminal question concerns the origin of Phase X and its relationship with the polar nanoregions. Starting from the diffuse scattering intensity measurements of Vakhrushev *et al.* on

PMN, [20] Hirota *et al* proposed an entirely new model of the PNR. [21] When ionic displacements due to a normal ferroelectric distortion are determined from measurements of Bragg intensities below T_c , the point of reference (origin) for these displacements is arbitrary. Only the relative positions between the atoms are meaningful. But in the case of the diffuse scattering in PMN, which first appears several hundred degrees above T_c , the origin is not arbitrary because the surrounding lattice is still cubic. Following this reasoning, a simple inspection of the displacements given by Vakhrushev *et al.* shows that the PNR center-of-mass is shifted from that of surrounding cubic phase. An approximate representation of this shift is shown in Fig. 4. One logical way to interpret the PMN displacements is to view them as the sum of a center-of-mass (COM) conserving component, and a scalar shift δ that is the same for all atoms. Using this approach Hirota *et al.* demonstrated that the COM-conserving ionic displacements match the ionic motions associated with the soft TO mode, first observed above the Burns temperature T_d , [22] thus lending strong experimental support to this interpretation. The uniform shift of the PNR has since been suggested to be the result of the coupling between the soft TO mode and the TA mode (first appreciated by Naberezhnov *et al.* [16]). In this case the soft coupled TO mode will necessarily carry an acoustic component that could explain the uniform shift. [23, 24]

The essential point is that the uniform shift of the PNR, which is of order 60% that of the Pb displacement, combined with their large ($\approx 30 - 50 \text{ \AA}^3$) size, makes the process of *melting* the PNR into the surrounding ferroelectric phase exceedingly difficult, and thus immensely slow. In this respect we believe it is the shift δ that stabilizes Phase X. While more study is needed to characterize the PNR, and to determine the microscopic origin of the displacement δ , we believe that these ideas form the basis of an elegant and self-consistent model in which it is possible to understand the basic properties of these lead-oxide relaxors.

We thank A. Bokov, T. Egami, K. Hirota, K. Ohwada, C. Stock, D. Vanderbilt, S. Wakimoto, and G. Xu, for stimulating discussions. We also acknowledge financial support from the U. S. Dept. of Energy under contract No. DE-AC02-98CH10886, and the Office of Naval Research, Grant No. N00014-99-1-0738.

-
- [1] P. Bonneau, P. Garnier, E. Husson, and A. Morell, *Mater. Res. Bull.* **24**, 201 (1989); P. Bonneau, P. Garnier, G. Calvarin, E. Husson, J.R. Gavarri, A.W. Hewat, and A. Morell, *J. Solid State Chem.* **91**, 350 (1991).
 - [2] N. de Mathan, E. Husson, G. Calvarin, J. R. Gavarri, A. W. Hewat, and A. Morell, *J. Phys.: Condens. Matter* **3**, 8159 (1991).

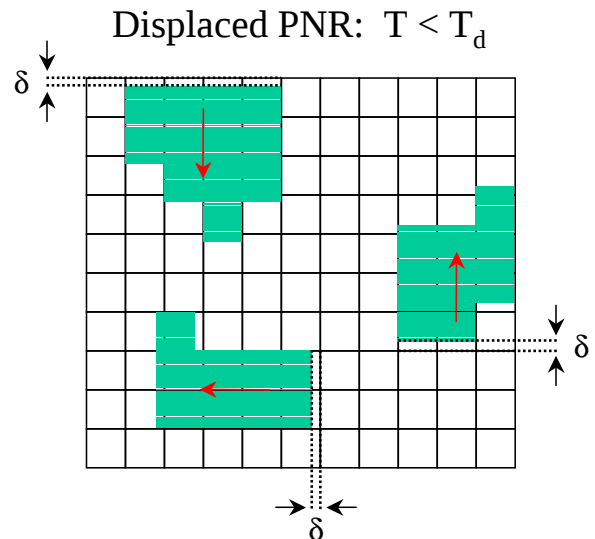


FIG. 4: Schematic diagram of the polar nanoregions shown in green. White squares refer to the underlying perovskite cubic lattice. The PNR are displaced relative to the cubic lattice by an amount δ , shown by the dotted lines, in the direction of the PNR polar axis shown as red arrows.

- [3] Z.-G. Ye, *Key Engineering Materials Vols. 155-156*, 81 (1998).
- [4] S. W. Choi, T. R. Shrout, S. J. Jang, A. S. Bhalla, *Ferroelectrics* **100**, 29 (1989).
- [5] B. Noheda, D. E. Cox, G. Shirane, J. Gao, and Z.-G. Ye, *Phys. Rev. B* **66**, 054104 (2002).
- [6] J. Kuwata, K. Uchino, S. Nomura, *Ferroelectrics* **37**, 579 (1981).
- [7] D. La-Orautapong, B. Noheda, Z.-G. Ye, P. M. Gehring, J. Toulouse, D. E. Cox, and G. Shirane, *Phys. Rev. B* **65**, 144101 (2002).
- [8] Z.-G. Ye, Y. Bing, J. Gao, A. A. Bokov, P. Stephens, B. Noheda, and G. Shirane, *Phys. Rev. B* **67**, 104104 (2003).
- [9] A. Lebon, H. Dammak, G. Calvarin, and I. Ould Ahmedou, *J. Phys.: Condens. Matter* **14**, 7035 (2002).
- [10] B. Dkhil, J. M. Kiat, G. Calvarin, G. Baldinozzi, S.B. Vakhrushev, and E. Suard, *Phys. Rev. B* **65**, 024104 (2001).
- [11] K. Ohwada, K. Hirota, P. W. Rehrig, Y. Fujii, and G. Shirane, *cond-mat/0207726*.
- [12] G. Xu, Z. Zhong, Y. Bing, Z.-G. Ye, C. Stock, and G. Shirane, *Phys. Rev. B* **67**, 104102 (2003).
- [13] Our choice of beam collimations were based on Monte Carlo intensity simulations performed by Vinita Ghosh.
- [14] J. E. Lorenzo *et al.*, *Phys. Rev. B* **50**, 1278 (1994).
- [15] W. Chen and Z.-G. Ye, unpublished; Z.-G. Ye, P. Tissot, and H. Schmid, *Mater. Res. Bull.*, **25**, 739 (1990).
- [16] A. Naberezhnov, S. B. Vakhrushev, B. Dörner, and H. Moudén, *Eur. Phys. J. B* **11**, 13 (1999).
- [17] G. Burns and F. H. Dacol, *Solid State Commun.* **48**, 853 (1983); *ibid*, *Phys. Rev. B* **28**, 2527 (1983).
- [18] S. Wakimoto, C. Stock, R. J. Birgeneau, Z.-G. Ye, W. Chen, W. J. L. Buyers, P. M. Gehring, and G. Shirane, *Phys. Rev. B* **65**, 172105 (2002).
- [19] C. Stock, R. J. Birgeneau, S. Wakimoto, J. S. Gardner, W. Chen, Z.-G. Ye, and G. Shirane, *cond-mat/0301132*.

- [20] S. B. Vakhrushev, B. E. Kvyatkovksy, A. A. Naberezhnov, N. M. Okuneva, and B. Toperverg, *Ferroelectrics* **90**, 173 (1989).
- [21] K. Hirota, Z.-G. Ye, S. Wakimoto, P. M. Gehring, and G. Shirane, *Phys. Rev. B* **65**, 104105 (2002).
- [22] P. M. Gehring, S. Wakimoto, Z.-G. Ye, and G. Shirane, *Phys. Rev. Lett.* **87**, 277601 (2001).
- [23] Y. Yamada and T. Takakura, cond-mat/0209573.
- [24] S. Wakimoto, C. Stock, Z.-G. Ye, W. Chen, P. M. Gehring, and G. Shirane, *Phys. Rev. B* **66**, 224102 (2002).